

Effects of Magnetic Order on the Upper Critical Field of UPt_3

J.A. Sauls

Department of Physics & Astronomy, Northwestern University, Evanston, IL 60208

(December 13, 1994)

Abstract

I present a Ginzburg-Landau theory for hexagonal oscillations of the upper critical field of UPt_3 near T_c . The model is based on a 2D representation for the superconducting order parameter, $\vec{\eta} = (\eta_1, \eta_2)$, coupled to an in-plane AFM order parameter, $\vec{m}_s$. Hexagonal anisotropy of H_{c2} arises from the weak in-plane anisotropy energy of the AFM state and the coupling of the superconducting order parameter to the staggered field. The model explains the important features of the observed hexagonal anisotropy [N. Keller, *et al.*, Phys. Rev. Lett. **73**, 2364 (1994).] including: (i) the small magnitude, (ii) persistence of the oscillations for $T \rightarrow T_c$, and (iii) the change in sign of the oscillations for $T > T^*$ and $T < T^*$ (the temperature at the tetracritical point). I also show that there is a low-field crossover (observable only very near T_c) below which the oscillations should vanish.

I. INTRODUCTION

The heavy Fermion superconductor UPt_3 has attracted a great deal of attention because of its remarkable low temperature phase diagram. The key features are: (i) the existence of two superconducting phases in zero field with a small separation of the transition temperatures, $\Delta T_c \simeq 50 \text{ mK}$, compared to $T_c \simeq 500 \text{ mK}$, (ii) the existence of three superconducting phases in a magnetic field (iii) with phase boundaries that meet at a tetracritical point (T^*, H^*) on the upper critical field line. [1,2] Interpretations of this phase diagram fall into two main categories of theoretical models: (i) theories based on two symmetry un-related order parameters which are accidentally nearly degenerate, [3,4] and (ii) models based on a single multi-component order parameter belonging to a higher dimensional representation in which the degeneracy is lifted by a weak symmetry breaking field (SBF). [5–10] UPt_3 is a close-packed hexagonal crystal with two formula units per unit cell; the point group is D_{6h} . Two candidates for an intrinsic SBF have been identified experimentally. Neutron scattering experiments show that UPt_3 develops an anti-ferromagnetic order parameter, $\vec{m}_s \perp \hat{c}$, below a Néel temperature of $T_N \simeq 5 \text{ K}$. [11] The magnitude of the ordered moment is small, $\sim 0.02\mu_B$ per U atom, and is directed in the basal plane thus breaking the in-plane hexagonal symmetry. Evidence in support of an AFM symmetry breaking field was found from pressure studies of the superconductivity and AFM order. Heat capacity measurements show that the splitting of the superconducting transitions is suppressed under a hydrostatic pressure of $p_c \simeq 3.8 \text{ kbar}$, [12] while neutron scattering measurements show the suppression of AFM order at roughly the same pressure, $p_* \simeq 3.2 \text{ kbar}$. [13] However, the observed magnetic Bragg peaks indicate finite-range AFM order with a correlation length $\xi_{afm} \simeq 250 \text{ \AA}$ depending on the crystal, which has led to discussion of whether or not the AFM order is intrinsic property of UPt_3 . [14] Alternatively, a macroscopic strain field was proposed [15] as a possible SBF based on the experimental observation of a complex incommensurate structural modulation in UPt_3 with characteristic wavelengths of order 10-50 lattice spacings and typical domain sizes of order $10^4 \text{ \AA}$. However, these structural modulations seem unlikely to be the principal SBF responsible for the double transition since the high formation temperature suggests that they persist to pressures well above that required to destroy the double transition and the AFM order. [16]

In a recent article, Keller, *et al.* [17] reported the observation of a weak hexagonal modulation of the upper critical field of UPt_3 as a function of the orientation of the field in the basal plane. The key features of these measurements are: (i) the small magnitude of the oscillations, $|\delta H_{c2}^{hex}/H_{c2}| \lesssim 0.02$, (ii) persistence of the oscillations for $T \rightarrow T_c$, and (iii) the change in sign of the oscillations for $T > T^*$ and $T < T^*$, where T^* is the temperature at the tetracritical point. In this paper I show that hexagonal oscillations such as these

are a consequence of the in-plane AFM symmetry breaking field above T_c that is responsible for the double transition in UPt₃.

II. PERFECT HEXAGONAL SYMMETRY

In order to sharpen the argument I briefly review the important theoretical results on the anisotropy of the in-plane upper critical field in *any* perfectly hexagonal superconductor. First consider a hexagonal superconductor described by a one-component order parameter, η . This case includes conventional superconductors for which η is invariant under D_{6h} , as well as unconventional cases where η changes sign under one or more symmetry operations. In the Ginzburg-Landau (GL) limit the free energy functional for any superconducting order parameter belonging to a one-dimensional representation is

$$\mathcal{F} = \alpha(T)|\eta|^2 + \beta|\eta|^4 + \kappa_{||}(D_i\eta)(D_i\eta)^* + \kappa_{\perp}(D_z\eta)(D_z\eta)^*, \quad (1)$$

where $D_i = \nabla_i + 2e/\hbar c A_i$ and repeated indices are summed over (x, y) . An important point here is that the GL functional has an accidental symmetry; to second order in the gradients there are no terms in the functional that differentiate hexagonal symmetry (D_{6h}) from cylindrical symmetry ($D_{\infty h}$). Consequently, the upper critical field is independent of the orientation of $\vec{H}$ in the basal plane; $H_{c2}^{\perp} = \frac{\hbar c}{2e}|\alpha(T)|/\sqrt{\kappa_{||}\kappa_{\perp}} \sim (1 - T/T_c)$. Hexagonal anisotropy of $H_{c2}^{\perp}$ shows up only at lower temperature when higher-order gradients become significant. The lowest-order contribution to the free energy functional that is invariant under D_{6h} , but not $D_{\infty h}$, is

$$\mathcal{F}_{hex} = \kappa_6 |(D_x + iD_y)^3\eta|^2. \quad (2)$$

It is straight-forward to show that this term leads to hexagonal oscillations of $H_{c2}^{\perp}(T)$ of the form,

$$\delta H_{c2}^{\perp}(\vartheta, T) \propto \kappa_6 (1 - T/T_c)^3 * \cos(6\vartheta), \quad (3)$$

to leading order in κ_6 . The key point is that the hexagonal anisotropy vanishes as $(1 - T/T_c)^3$ as $T \rightarrow T_c$. This result is not limited to superconductors with a one-dimensional order parameter.

Burlachkov [18] showed that $H_{c2}^{\perp}$ is isotropic for fields in the basal plane, in the GL limit, for *any* of the two-dimensional representations of D_{6h} . In this case the GL functional can be written as

$$\begin{aligned} \mathcal{F}_{sc} = & \alpha(T)|\eta_i|^2 + \beta_1|\eta_i|^4 + \beta_2|\eta_i^2|^2 + \kappa_4(D_z\eta_i)(D_z\eta_i)^* \\ & + \kappa_1(D_i\eta_j)(D_i\eta_j)^* + \kappa_2(D_i\eta_i)(D_j\eta_j)^* + \kappa_3(D_i\eta_j)(D_j\eta_i)^*, \end{aligned} \quad (4)$$

where the order parameter (η_1, η_2) transforms according to one of the 2D irreducible representations (E_1 or E_2) of D_{6h} . The isotropy of $H_{c2}^{\perp}$ in the GL limit again follows because to second-order in the gradients and in (η_1, η_2) the GL functional is invariant under the larger group, $D_{\infty h}$. Again, one has to examine sixth-order terms (therefore, of order $(1 - T/T_c)^3$) in order to develop hexagonal anisotropy in $H_{c2}^{\perp}$. [19]

Recently, Mineev examined GL models based on two accidentally nearly degenerate 1D representations. [20] Such a models have been investigated by several authors [3,4] as candidate theories of the H-T phase diagram of UPt₃. An important feature of these models is that they do not rely on the coupling of the order parameter to a SBF that reflects a weak breaking of hexagonal symmetry above T_c . The basic result for the anisotropy of $H_{c2}^{\perp}$ is the same; hexagonal oscillations vanish as $(1 - T/T_c)^3$ near T_c . [20] Thus, the experimental observation of hexagonal oscillations of $H_{c2}^{\perp}$ in UPt₃ for $T \rightarrow T_c$ is in conflict with any GL model of the superconducting phases that is based on perfect hexagonal symmetry above T_c .

Below I show that hexagonal oscillations of $H_{c2}^{\perp}(T)$ do appear in the GL limit ($T \approx T_c$) for the class of models based on a 2D superconducting order parameter coupled to an AFM symmetry breaking field present above T_c . It may initially seem odd that one obtains six-fold oscillations from an AFM order parameter that *reduces* the symmetry from hexagonal to orthorhombic. Six-fold oscillations of $H_{c2}^{\perp}$ are shown to be a natural consequence of a small in-plane anisotropy energy of the AFM order parameter, while orthorhombic anisotropy of H_{c2} appears in the limit of large in-plane anisotropy.

III. BROKEN SYMMETRY MODEL

The free energy functional for a 2D superconducting order parameter, $\vec{\eta}$, coupled to an AFM order parameter, $\vec{m}_s$, is the sum of (i) $\mathcal{F}_{sc}$, which represents the GL functional for the superconducting order parameter, (ii) $\mathcal{F}_{afm}$, which is the free energy for the AFM phase above T_c , and (iii) $\mathcal{F}_{sc-afm}$, which represents the coupling between superconductivity and anti-ferromagnetism. The general form for the superconducting GL functional in the absence of a SBF has been discussed by many authors [21], and is given in eq. 4. First, consider the magnetic free energy above T_c .

A. Free Energy of the AFM state above T_c

For $T < T_N$ the mean-field approximation for the magnetic free energy functional should be reliable provided the correct magnetic ordering has been identified. I assume an order parameter, $\vec{m}_s = (m_x, m_y, m_z)$, describing AFM correlations between neighboring U atoms in a double unit cell, and start from a Landau functional for the magnetic free energy density,

$$\mathcal{F}_{afm} = a(T)|\vec{m}_s|^2 + b|\vec{m}_s|^4 + \dots + a_z m_z^2 + c' \text{Re}(m_x + im_y)^6 + g(\vec{m}_s \cdot \vec{H})^2. \quad (5)$$

The first line of terms is invariant under the full spin-rotation group. They are primarily due to exchange interactions in typical magnetic materials. Thus, neglecting the anisotropy terms, one has $m_0 = \sqrt{|a(T)|/2b} \propto |T - T_N|^{1/2}$ for the magnitude of the AFM order parameter in the exchange approximation.

The third term represents the leading order uniaxial anisotropy energy. Anisotropy energies arise from spin-orbit interactions and are typically small compared to the exchange terms. I assume $a_z > 0$ which favors in-plane AFM order.

The sixth-order term in $\vec{m}_s$ is the leading term in a GL expansion for the in-plane anisotropy energy. The in-plane anisotropy energy is assumed to be a small perturbation to the AFM exchange energy, *i.e.*

$$U_{anis} = c' m_0^6 \ll U_{exch} = \frac{1}{2} |a(T)| m_0^2. \quad (6)$$

In the absence of an external field the in-plane anisotropy energy leads to six degenerate minimum energy orientations for $\vec{m}_s$, which are equivalent to three commensurate wavevectors in a spin-density wave description. There are two sets of preferred orientations depending on the sign of the coefficient c' . If $c' > 0$ the moments prefer the set of alignments, $\{\vartheta_n = n\pi/3 + \pi/6; n = 0, \dots, 5\}$ that includes the $\vec{a}^*$ axis, while for $c' < 0$ the set of minimum energy orientations are shifted by $\pi/6$, and includes the $\vec{a}$ axis [I use the notation in Ref. [17]].

The Zeeman energy is quadratic in $\vec{H}$ for an antiferromagnet and prefers the AFM order parameter to be aligned perpendicular to the field ($g > 0$). [22] Thus, for a general orientation of the field in the basal plane there is competition between the anisotropy energy and the Zeeman energy. The field at which the anisotropy energy is comparable to the Zeeman energy defines a cross-over field scale,

$$H_{anis} = \sqrt{\frac{c'}{g}} m_0^2. \quad (7)$$

At low fields, $H \ll H_{anis}$, the AFM order parameter is essentially locked by the in-plane anisotropy energy to an equilibrium orientation, ϑ_n . However, for $H > H_{anis}$ the Zeeman energy dominates the anisotropy energy and the orientation of the magnetization will adjust to remain approximately perpendicular to $\vec{H}$. This case is particularly relevant to the discussion of the hexagonal oscillations of H_{c2} . In the limit $H \gg H_{anis}$ the orientation of $\vec{m}_s$ is fixed by the field, $\vartheta = \vartheta_H - \pi/2$, or $\vec{m}_s = m_s(\sin \vartheta_H, -\cos \vartheta_H)$. The magnitude of the staggered moment is then to a very good approximation determined by minimizing the AFM free energy

$$\mathcal{F}_{afm} = a(T) m_s^2 + b m_s^4 - c' m_s^6 \cos(6\vartheta_H), \quad (8)$$

at *fixed* orientation $\vartheta = \vartheta_H - \pi/2$. Treating the anisotropy energy as a perturbation leads to a small correction to the exchange approximation for the AFM order parameter; $m_s = m_0 + \delta m_s$. Retaining the leading order corrections to the stationarity condition gives a hexagonal modulation of the AFM order parameter,

$$\frac{\delta m_s}{m_0} = \frac{3}{4} \left(\frac{U_{anis}}{U_{exch}} \right) \cos(6\vartheta_H), \quad H \gg H_{anis}. \quad (9)$$

This modulation of the AFM order parameter by the anisotropy potential leads to a hexagonal modulation of the upper critical field in the SBF model for the double superconducting transition.

B. Coupling between Superconductivity and AFM

I assume a specific 2D model, based on an E_2 order parameter, which I discussed recently in the context of the H-T phase diagram. [10] In this model the gradient coefficients $\kappa_2 = \kappa_3 \simeq 0$ for weak hexagonal anisotropy;¹ however, for in-plane magnetic fields the principal arguments that follow apply to any of the 2D models. The parameters of the GL functional in eq. 4 are calculated from Fermi-liquid theory. [23,24] The gradient coefficients, $\kappa_1 \simeq N_f(v_f^\perp)^2/(\pi T_c)^2$ and $\kappa_4 \simeq N_f(v_f^\parallel)^2/(\pi T_c)^2$, are determined by the density of states, N_f , and the anisotropic components of the Fermi velocity, $v_f^{\perp,\parallel}$. These coefficients determine the uniaxial anisotropy of H_{c1} and H_{c2} . The other coefficients, $\alpha(T) = N_f(T - T_c)$ and $\beta_2 = \frac{1}{2}\beta_1 = \frac{7\zeta(3)N_f}{16\pi^2 T_c^2}$, determine the condensation energy; T_c is the transition temperature in absence of coupling to the AFM order parameter.

To calculate the hexagonal anisotropy of H_{c2} near T_c I need the the terms in the free energy that describe the coupling of the superconductivity to the AFM order parameter. The leading order symmetry breaking terms are [5,6,10]

$$\begin{aligned} \mathcal{F}_{sc-afm} = & -\epsilon m_s^2 N_f T_c (|\eta_1|^2 - |\eta_2|^2) \\ & + \epsilon_\perp m_s^2 \kappa_1 (|\vec{D}_\perp \eta_1|^2 - |\vec{D}_\perp \eta_2|^2) \\ & + \epsilon_\parallel m_s^2 \kappa_4 (|D_z \eta_1|^2 - |D_z \eta_2|^2). \end{aligned} \quad (10)$$

The first term is responsible for the double transition in zero field, while the gradient terms generate an asymmetry in the slopes of the two branches of H_{c2} for $T > T^*$ and $T < T^*$.

Combining the coupling terms with the superconducting free energy (eq. 4) gives,

$$\begin{aligned} \mathcal{F}_{sc} + \mathcal{F}_{sc-afm} = & \alpha_+(T)|\eta_1|^2 + \alpha_-(T)|\eta_2|^2 \\ & + \kappa_1^+ (\vec{D}_\perp \eta_1) \cdot (\vec{D}_\perp \eta_1)^* + \kappa_1^- (\vec{D}_\perp \eta_2) \cdot (\vec{D}_\perp \eta_2)^* \\ & + \kappa_4^+ (D_z \eta_1)(D_z \eta_1)^* + \kappa_4^- (D_z \eta_2)(D_z \eta_2)^*, \end{aligned} \quad (11)$$

with $\alpha_\pm(T) = N_f(T - T_c^\pm)$. The fourth-order terms are omitted since they are not relevant to the determination of H_{c2} . The SBF field generates a splitting of T_c and the gradient coefficients,

$$T_c^\pm = T_c (1 \pm \epsilon m_s^2) \quad ; \quad \kappa_{1,4}^\pm = \kappa_{1,4} (1 \pm \epsilon_{\perp,\parallel} m_s^2). \quad (12)$$

The upper critical field is obtained from solutions of the linearized GL equations,

¹In this context the term ‘weak hexagonal anisotropy’ refers to the Fermi surface. This anisotropy is the origin of the hexagonal anisotropy of $H_{c2}^\perp(T)$ in perfect hexagonal systems, which vanishes for $T \rightarrow T_c$ as $(1 - T/T_c)^3$. This same Fermi surface anisotropy is responsible for the deviation of $\kappa_{2,3}$ from zero in the E_2 representations. [10]

$$\begin{aligned}\kappa_1^+ \vec{D}_\perp^2 \eta_1 + \kappa_4^+ D_z^2 \eta_1 &= \alpha_+(T) \eta_1, \\ \kappa_1^- \vec{D}_\perp^2 \eta_2 + \kappa_4^- D_z^2 \eta_2 &= \alpha_-(T) \eta_2.\end{aligned}\tag{13}$$

The resulting value of $H_{c2}^\perp(T)$ is then the larger value of the solutions for the two branches,

$$H_{c2}^\pm(T; \vartheta_H) = \frac{\hbar c}{2e} \frac{N_f (T_c^\pm(\vartheta_H) - T)}{\sqrt{\kappa_1^\pm \kappa_4^\pm}}.\tag{14}$$

For $\kappa_1^+ \kappa_4^+ > \kappa_1^- \kappa_4^-$ the upper critical field has a kink at the temperature T^* (tetracritical point). The solution H_{c2}^+ denotes the branch with $T > T^*$ and H_{c2}^- denotes the branch with $T < T^*$. The two branches correspond to transitions from the normal state to a superconducting state with order parameters, $\vec{\eta} \sim (1, 0)$ for $T > T^*$ and $\vec{\eta} \sim (0, 1)$ for $T < T^*$. Note that $H_{c2}^\pm(T)$ depends implicitly on the orientation of the field, ϑ_H , through the AFM order parameter m_s .

Hexagonal oscillations of $H_{c2}^\perp(T)$ result from the modulation of the AFM order parameter by the sixth-order anisotropy energy. In the limit $H \gg H_{anis}$, the extrapolation points, $T_c^\pm(\vartheta_H)$, show a hexagonal modulation. The modulation can be scaled in units of the zero-field splitting of the transition, $\Delta T_c/T_c = \epsilon m_0^2 (1 + \beta_1/\beta_2)$, and the ratio of the anisotropy energy to the exchange energy,

$$T_c^\pm(\vartheta_H) = T_c^\pm \pm \frac{3}{2} \frac{\Delta T_c}{1 + \beta_1/\beta_2} \left(\frac{U_{anis}}{U_{exch}} \right) [\cos(6\vartheta_H) - 1].\tag{15}$$

The parameters $T_c^\pm$ (without arguments) denote the extrapolation points in zero field. Note that the modulation of the two extrapolation points, T_c^+ and T_c^- , is out of phase by 180° . This explains the change in phase of the oscillations of $H_{c2}^\perp(T)$ for temperatures above and below the tetracritical point. Figure 1 shows the upper critical field for two orientations of the magnetic field. Note the change in $H_{c2}^\perp(T)$ upon rotating the field from $\vartheta_H = 0$ (minimum of the anisotropy energy) to $\vartheta_H = \pi/6$ (maximum of the anisotropy energy). This change in phase of the oscillations for $T > T^*$ and $T < T^*$ has the same origin as the splitting of T_c in zero field by the AFM symmetry breaking field.²

The oscillations are small in magnitude,

$$|\delta H_{c2}^\pm|_{max} = \frac{1}{2} |H_{c2}^\pm(\vartheta_H = 0) - H_{c2}^\pm(\vartheta_H = \pi/6)| \simeq \left| \frac{dH_{c2}^\pm}{dT} \right| * \frac{3}{2} \frac{\Delta T_c}{(1 + \beta_1/\beta_2)} \left(\frac{U_{anis}}{U_{exch}} \right),\tag{16}$$

and weakly dependent on temperature, except for $T \approx T^*$, where the oscillations change sign (see Fig. 1), and for temperatures *very* close to T_c where $H_{c2}(T)$ drops below the anisotropy field, H_{anis} . From the magnitude of the hexagonal anisotropy measured by Keller, *et al.* [25], $|\delta H_{c2}|_{max} \simeq 10^{-3}$ T for $T \simeq 507$ mK $> T^* \simeq 430$ mK, one obtains an estimate for the ratio of the anisotropy energy to the exchange energy. Taking $\Delta T_c \simeq 60$ mK, $dH_{c2}^+/dT \simeq 4.5 \times 10^{-3}$ T/mK, [25] gives $U_{anis}/U_{exch} \simeq 0.015$.

In addition to the modulation of the extrapolation temperatures, the slopes of the two branches of $H_{c2}(T)$, are modulated by the anisotropy potential,

$$S^\pm(\vartheta_H) = -dH_{c2}^\pm/dT = S^\pm \left(1 \mp (\epsilon_\parallel + \epsilon_\perp) m_0^2 \frac{3}{4} \left(\frac{U_{anis}}{U_{exch}} \right) [\cos(6\vartheta_H) - 1] \right),\tag{17}$$

where $S^\pm$ is the slope corresponding to a minimum of the anisotropy energy. These terms generate temperature dependent amplitudes for the oscillations of the two branches of $H_{c2}^\perp(T)$ as shown in Fig. 1.

²Note that Fig. 1 includes the additional corrections discussed in the next section; however, the dominant effect is the modulation of the extrapolation temperatures by the anisotropy energy.

C. Higher-order corrections at lower fields

The oscillations of $H_{c2}^\perp(T)$ obtained above are for fields large compared to the anisotropy field, H_{anis} . While it is reasonable to assume that H_{anis} is very low, it is non-zero and so provides a cross-over field below which the hexagonal oscillations of $H_{c2}^\perp$ should vanish. For $H > H_{anis}$ there are also corrections to the ‘high-field’ limit discussed above. These corrections, as well as the low-field cross-over behavior, are obtained from the minimization of the AFM free energy functional with respect to both m_s and ϑ for fixed ϑ_H . The stationarity condition $\delta\mathcal{F}_{afm}/\delta m_s = 0$ generates,

$$\frac{\delta m_s}{m_0} = -\frac{3}{4} \left(\frac{U_{anis}}{U_{exch}} \right) \left\{ \cos(6\vartheta) + \frac{1}{3} \left(\frac{H}{H_{anis}} \right)^2 \cos^2(\vartheta_H - \vartheta) \right\}, \quad (18)$$

to leading order in U_{anis}/U_{exch} . The second term in eq. 18 originates from the Zeeman energy. The relation between the orientation of the applied field (ϑ_H) and that of the AFM order parameter (ϑ) is determined by the stationarity condition $\delta\mathcal{F}_{afm}/\delta\vartheta = 0$,

$$\sin(6\vartheta) = \frac{1}{6} \left(\frac{H}{H_{anis}} \right)^2 \sin(2(\vartheta_H - \vartheta)). \quad (19)$$

In the zero-field limit one obtains the expected result that the AFM order parameter is locked to the lattice at the minima of the anisotropy energy given by $n\pi/3 + \pi/6$ for $c' > 0$; the solutions $n\pi/3$ correspond to maxima of the anisotropy energy. In the opposite limit, $H_{anis}/H \rightarrow 0$, the AFM order parameter is oriented at $\pm\pi/2$ relative to the field; the other solutions at $\pm\pi$ correspond to maxima of the Zeeman energy.

For $H_{anis}/H \ll 1$ the orientation of $\vec{m}_s$ is no longer strictly orthogonal to $\vec{H}$. The deviation, $\beta = (\vartheta_H - \vartheta) - \pi/2$, oscillates with an amplitude proportional to $(H_{anis}/H)^2$,

$$\beta \simeq 3 \left(\frac{H_{anis}}{H} \right)^2 \sin(6\vartheta_H). \quad (20)$$

This phase shift vanishes near a minimum of the anisotropy energy and is maximum at orientations of $\vec{H}$ corresponding to a maximum in the slope of the anisotropy energy (*i.e.* maximum anisotropy torque on $\vec{m}_s$). This correction, combined with the correction from the Zeeman energy, gives

$$\frac{\delta m_s}{m_0} = \frac{3}{4} \left(\frac{U_{anis}}{U_{exch}} \right) f(\vartheta_H), \quad (21)$$

$$f(\vartheta_H) = \cos \left(6\vartheta_H - 18 \left(\frac{H_{anis}}{H} \right)^2 \sin(6\vartheta_H) \right) - 3 \left(\frac{H_{anis}}{H} \right)^2 \sin^2(6\vartheta_H), \quad (22)$$

for the modulation of the AFM order parameter parameter. The corrections from the Zeeman energy and the angular deviation from $\pi/2$ generate non-sinusoidal hexagonal oscillations of $H_{c2}(T)$. Figure 2 shows these oscillations for temperatures above and below T^* . Note the sharpening of the oscillations for $\vec{H}||\vec{a}^*$ ($\vartheta_H = \pi/6$). A similar effect is also seen in the experimental results for $H_{c2}^\perp(T)$ reported by Keller, *et al.* [25]

At very low fields, $H < H_{anis}$, and therefore at temperatures very near T_c (*i.e.* $|T - T_c| < H_{anis}/|dH_{c2}^+/dT|$), the hexagonal oscillations of $H_{c2}^\perp$ disappear. The AFM order parameter becomes locked to the lattice by the in-plane anisotropy energy as $H \rightarrow 0$. For $H \ll H_{anis}$, the Zeeman energy is a perturbation and leads to small deviations of $\vec{m}_s$ from the minima of the anisotropy energy. Assuming that $\vec{m}_s$ is oriented at $\vartheta = \pi/6$ in zero field (corresponding to a minimum along the $\vec{a}^*$ axis), the perturbed orientation of $\vec{m}_s$ at finite $\vec{H}$ is,

$$\vartheta = \pi/6 - \frac{1}{36} \left(\frac{H}{H_{anis}} \right)^2 \sin(2\vartheta_H - \pi/3). \quad (23)$$

This deviation leads to an *orthorhombic* modulation of the AFM order parameter,

$$\frac{\delta m_s}{m_0} = \frac{3}{4} \left(\frac{U_{anis}}{U_{exch}} \right) \left[1 - \frac{1}{3} \left(\frac{H}{H_{anis}} \right)^2 \cos^2(\vartheta_H - \pi/6) \right], \quad H \ll H_{anis}. \quad (24)$$

For $H_{c2}(T) \ll H_{anis}$ and $\vartheta_H - \pi/6 \neq \pm\pi/2$ the upper critical field line bends towards the zero-field transition temperature, T_{c+} ,

$$H_{c2}(T) = S^+ \left[(T_c^+ - T) - \frac{3}{2} \left(\frac{\Delta T_c}{1 + \beta_1/\beta_2} \right) \left(\frac{U_{anis}}{U_{exch}} \right) \left(\frac{S^+(T_c^+ - T)}{H_{anis}} \right)^2 \cos^2(\vartheta_H - \pi/6) \right]. \quad (25)$$

In conclusion, I have developed a Ginzburg-Landau theory for the upper critical field anisotropy of UPt₃ based on a superconducting order parameter belonging to a two-dimensional representation coupled to an in-plane AFM order parameter. The key terms responsible for the hexagonal anisotropy of H_{c2} near T_c are the in-plane anisotropy and Zeeman energies of the AFM phase. These terms lead to hexagonal modulations of the AFM order parameter, which generate hexagonal anisotropy in $H_{c2}(T)$ through the SBF coupling to superconductivity. The GL theory accounts for the basic features of the observed oscillations, including the sign reversal at $T \approx T^*$.

IV. ACKNOWLEDGEMENTS

I acknowledge the support of the Aspen Center for Physics where this work developed, and the NSF through grant no. 9120521 for the Materials Research Center at Northwestern University. I thank V. P. Mineev and M. Zhitomirsky for their comments and critique, and especially M. Norman for important conversations. I also thank N. Keller for discussions and for sending me a copy of the work reported in Refs. [17,25] prior to publication.

-
- [1] G. Bruls *et al.*, Phys. Rev. Lett. **65**, 2294 (1990).
 - [2] S. Adenwalla *et al.*, Phys. Rev. Lett. **65**, 2298 (1990).
 - [3] I. Luk'yanchuk, J. de Phys. **11**, 1155 (1991).
 - [4] D. Chen and A. Garg, Phys. Rev. Lett. **70**, 1689 (1993).
 - [5] D. Hess, T. Tokuyasu, and J. Sauls, J. Phys. Condens. Matter **1**, 8135 (1989).
 - [6] K. Machida and M. Ozaki, J. Phys. Soc. Jpn. **58**, 2244 (1989).
 - [7] K. Machida and M. Ozaki, Phys. Rev. Lett. **66**, 3293 (1991).
 - [8] R. Joynt, Euro. Phys. Lett. **16**, 289 (1991).
 - [9] I. Luk'yanchuk and M. Zhitomirskii, Sov. Phys. JETP Lett. (1994).
 - [10] J. Sauls, Adv. Phys. **43**, 113 (1994).
 - [11] G. Aeppli *et al.*, Phys. Rev. Lett. **60**, 615 (1988).
 - [12] S. Hayden, L. Taillefer, C. Vettier, and J. Flouquet, Phys. Rev. **B46**, 8675 (1992).
 - [13] T. Trappmann, H. v. Löhneysen, and L. Taillefer, Phys. Rev. **B43**, 13714 (1991).
 - [14] T. Vorenkamp, Ph.D. thesis, University of Amsterdam, 1992.
 - [15] V. Mineev, Sov. Phys. JETP Lett. **57**, 683 (1993).
 - [16] P. A. Midgley *et al.*, Phys. Rev. Lett. **70**, 678 (1993).

- [17] N. Keller, J. L. Tholence, A. Huxley, and J. Flouquet, Phys. Rev. Lett. **73**, 2364 (1994).
- [18] L. Burlachkov, Sov. Phys. JETP **62**, 800 (1985).
- [19] V. Vinokour, J. A. Sauls, and M. Norman, unpublished (1994).
- [20] V. Mineev, preprint - August 1994 (1994).
- [21] M. Sigrist and K. Ueda, Rev. Mod. Phys. **63**, 239 (1991).
- [22] A. F. Andreev and V. I. Marchenko, Sov. Phys. Usp. **23**, 21 (1980).
- [23] P. Muzikar, D. Rainer, and J. A. Sauls, in *Cargese Lectures - 1993* (Kluwer Academic Press, 1993).
- [24] J. Sauls, in *Strongly Correlated Electronic Materials: The Los Alamos Symposium 1993*, edited by K. Bedell *et al.* (Academic Press, 1994).
- [25] N. Keller *et al.*, to appear in Proceedings of SCES94 (1994).

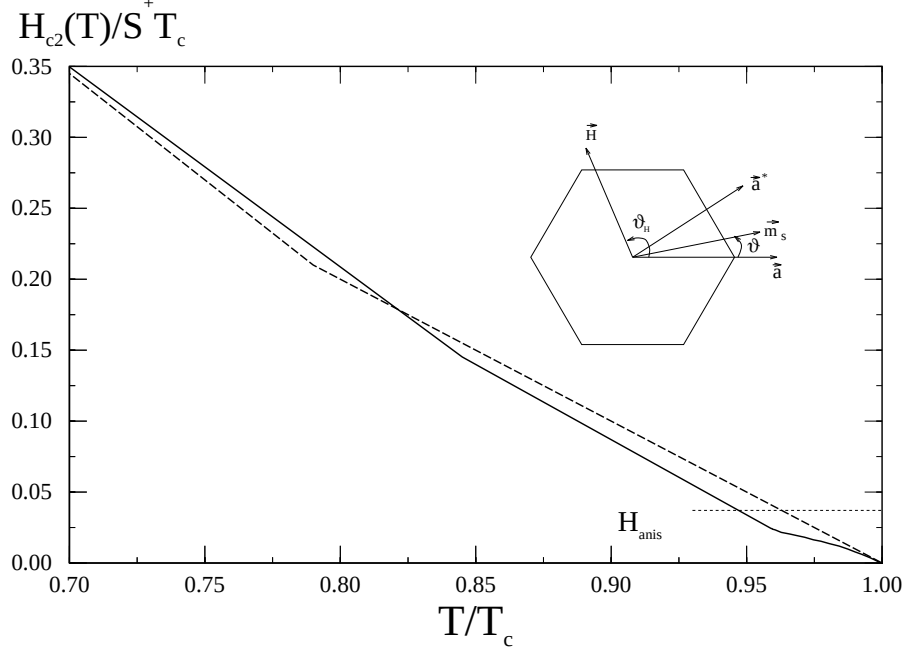


Fig. 1 Anisotropy of $H_{c2}^\perp(T)$ vs. T/T_c . The solid (dashed) curve is $H_{c2}^\perp(T)$ for $\vartheta_H = 0$ [$\vec{H} \parallel \vec{a}$] ($\vartheta_H = \pi/6$ [$\vec{H} \parallel \vec{a}^*$]). The cross-over occurs in the vicinity of $T^* \simeq 0.8T_c$. The magnitude of the anisotropy and the width of the transition region are amplified by the large value of $U_{anis}/U_{exch} = 0.2$ (chosen to show the anisotropy clearly in the graph). The other parameters are $S^-/S^+ = 1.5$, $\epsilon m_0^2 = 0.03$, $(\epsilon_{||} + \epsilon_{\perp})m_0^2 = 0.2$, $H_{anis}/S^+T_c = 0.04$. Below H_{anis} (dotted line) the curves merge at T_c (sketch).

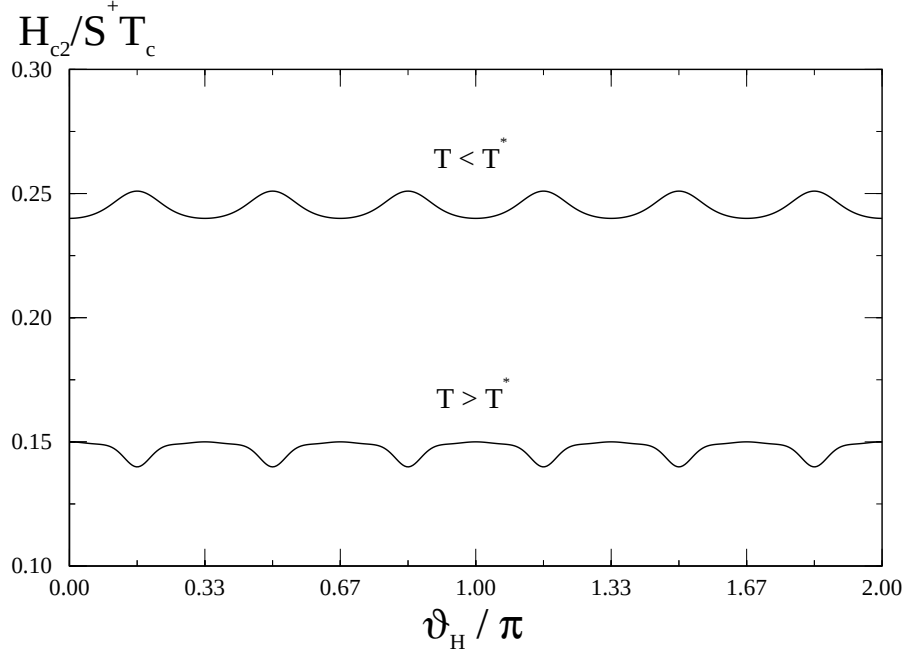


Fig. 2 Anisotropy of $H_{c2}^\perp(T)$ vs. ϑ_H . The angular dependence of H_{c2} shows the 180° relative phase of the oscillations for $T > T^*$ and $T < T^*$. The parameters are the same as those in Fig. 1. The scalloped shape of the oscillations arises from the deviation of $\vartheta_H - \vartheta$ from $\pi/2$.